

Table. 1

## The present invention

Claim (gel-cream agent)	(wt%)	
Indomethacin	0.1~3	A
Gelling agent	25~50	B
Oil Component	0.01~5	C
Water	7~30	D
Sorbitan monostearate	20~50	E
Glycerol monostearate		
Polyethylene glycol monostearate	0.01~10	F
Stearyl alcohol		

A: Active ingredient

B: Alcohol

C: Gelling agent

D: Oil component

E: Water

F: Surfactant

## Cited Document

Kimura JP 10-182458 Example 2 (External cream agent)	(wt%)	A+D+E+F
Indomethacin	1.0	A
Chlorpheniramine maleate	0.5	
Medium chain fatty acid triglyceride	20.0	D
Diisopropyl adipate	5.0	D
Propylene glycol	12.0	
Polyoxyethylene sorbitan monostearate	6.0	
Sorbitan monostearate	3.0	F
Glycerol monostearate	8.0	F
Purified water	Total 100	E

Kimura JP 10-182458 Example 3 (gel agent)	(wt%)	A+B+C+E+F
Indomethacin	0.5	A
Chlorpheniramine maleate	0.01	
Polyethylene glycol monostearate	5.0	F
Diisopropyl adipate	3.0	(D)
1,3-Butylene glycol	8.0	
Polyvinyl pyrrolidone	0.5	
Carboxyvinyl polymer	1.5	C
Diisopropanolamine	proper quantity	
Purified water	Total 100	E

Inagi US 4,309,414 Example 4 (gel agent)	(g)	A+B+C+E
Carboxyvinyl polymer	1.0	C
Hydroxyethylcellulose	1.0	
Indomethacin	1.0	A
Polyethylene glycol 300	10.0	
Diisopropyl adipate	2.0	(D)
Diisopropanolamine	0.9	
Purified water	Total 100	E

# Polyethylene Glycol

## 1. Nonproprietary Names

BP:	Macrogol 300
	Macrogol 400
	Macrogol 1000
	Macrogol 1540
	Macrogol 4000
	Macrogol 6000
JP:	Macrogol 20 000
	Macrogol 35 000
	Macrogol 400
	Macrogol 1500
PhEur:	Macrogol 4000
	Macrogol 6000
	Macrogol 20 000
	Macrogol 400
US:	Macrogol 1000
	Macrogol 1500
	Macrogol 3000
	Macrogol 4000
	Macrogol 6000
	Macrogol 20 000
US:	Macrogol 35 000
	Polyethylene glycol


## 2. Synonyms

Breox PEG; Carbowax; Hodag PEG; Lurol E; PEG; polyoxyethylene glycol.

## 3. Chemical Name and CAS Registry Number

$\alpha$ -Hydro- $\omega$ -hydroxy-poly(oxy-1,2-ethanediyl) [25322-68-3]

## 4. Empirical Formula Molecular Weight



Where  $n$  represents the average number of oxyethylene groups.

Alternatively, the general formula  $\text{H}(\text{OCH}_2\text{CH}_2)_n\text{OH}$  may be used to represent polyethylene glycol, where  $n$  is a number one more than the value of  $m$  in the previous formula.

See Table I for the average molecular weights of typical polyethylene glycols. Note that the number which follows PEG indicates the average molecular weight of the polymer.

## 5. Structural Formula




Table I: Structural formula and molecular weight of typical polyethylene glycol polymers.

Grade	m	Average molecular weight
PEG 200	4.2	190-210
PEG 300	6.4	285-315
PEG 400	8.7	380-420
PEG 540 (blend)	—	500-600
PEG 600	13.2	570-613
PEG 900	15.3	855-900
PEG 1000	22.3	950-1050
PEG 1450	32.5	1300-1600
PEG 1540	28-36	1300-1600
PEG 2000	40-50	1800-2200
PEG 3000	60-75	2700-3300
PEG 3350	75.7	3000-3700
PEG 4000	69-84	3000-4800
PEG 4600	104.1	4400-4800
PEG 8000	181.4	7000-9000

## 6. Functional Category

Ointment base; plasticizer; solvent; suppository base; tablet and capsule lubricant.

## 7. Applications in Pharmaceutical Formulation or Technology

Polyethylene glycols are widely used in a variety of pharmaceutical formulations including parenteral, topical, ophthalmic, oral, and rectal preparations.

Polyethylene glycols are stable, hydrophilic substances that are essentially nonirritant to the skin, see Section 14. Although they do not readily penetrate the skin, polyethylene glycols are water soluble and as such are easily removed from the skin by washing; they are therefore useful as ointment bases.<sup>(1)</sup> Solid grades are generally employed in topical ointments with the consistency of the base being adjusted by the addition of liquid grades of polyethylene glycol.

Mixtures of polyethylene glycols can be used as suppository bases<sup>(2)</sup> where they have the following advantages over fats: the melting point of the suppository can be made higher to withstand exposure to warmer climates; release of the drug is not dependent upon melting point; physical stability on storage is better; suppositories are readily miscible with rectal fluids. Disadvantages of using polyethylene glycols are: they are chemically more reactive than fats; greater care is needed in processing to avoid inelegant contraction holes in the suppositories; the rate of release of water-soluble medications decreases with the increasing molecular weight of the polyethylene glycol; polyethylene glycols tend to be more irritating to mucous membranes than fats.

Aqueous polyethylene glycol solutions can be used either as suspending agents or to adjust the viscosity and consistency of other suspending vehicles. When used in conjunction with other emulsifiers, polyethylene glycols can act as emulsion stabilizers.

Liquid polyethylene glycols are used as water-miscible solvents for the contents of soft gelatin capsules. However, they may cause hardening of the capsule shell by preferential absorption of moisture from gelatin in the shell.

In concentrations up to approximately 30% w/v, PEG 300 and PEG 400 have been used as the vehicle for parenteral dosage forms.

In solid-dose formulations, higher molecular weight polyethylene glycols can enhance the effectiveness of tablet binders and impart

plasticity to granules.<sup>(3)</sup> However, they have only limited binding action when used alone, and can prolong disintegration if present in concentrations greater than 5% w/w. When used for thermoplastic granulations,<sup>(4-6)</sup> a mixture of the powdered constituents with 10-15% w/w PEG 6000 is heated to 70-75°C. The mass becomes paste-like and forms granules if stirred while cooling. This technique is useful for the preparation of dosage forms such as lozenges when prolonged disintegration is required.

Polyethylene glycols can also be used to enhance the aqueous solubility or dissolution characteristics of poorly soluble compounds by making solid dispersions with an appropriate polyethylene glycol.<sup>(7)</sup> Animal studies have also been performed using polyethylene glycols as solvents for steroids in osmotic pumps.

In film coatings, solid grades of polyethylene glycol can be used alone for the film coating of tablets or can be useful as hydrophilic polishing materials. Solid grades are also widely used as plasticizers in conjunction with film-forming polymers.<sup>(7)</sup> The presence of polyethylene glycols, especially liquid grades, in film coats tends to increase their water permeability and may reduce protection against low pH in enteric-coating films. Polyethylene glycols are useful as plasticizers in microencapsulated products to avoid rupture of the coating film when the microcapsules are compressed into tablets.

Polyethylene glycol grades with molecular weights of 6000 and above can be used as lubricants, particularly for soluble tablets. The lubricant action is not as good as that of magnesium stearate, and stickiness may develop if the material becomes too warm during compression. An antiadherent effect is also exerted, again subject to the avoidance of over-heating.

In addition, polyethylene glycols have been used in the preparation of urethane hydrogels which are used as controlled-release agents.

## 8. Description

The USP describes polyethylene glycol as being an addition polymer of ethylene oxide and water. Polyethylene glycol grades 200-600 are liquids; grades 1000 and above are solids at ambient temperatures.

Liquid grades (PEG 200-600) occur as clear, colorless or slightly yellow-colored, viscous liquids. They have a slight, but characteristic odor and a bitter, slightly burning taste. PEG 600 can occur as a solid at ambient temperatures.

Solid grades (PEG >1000) are white or off-white in color, and range in consistency from pastes to waxy flakes. They have a faint, sweet odor. Grades of PEG 6000 and above are available as free-flowing milled powders.

## 9. Pharmacopelial Specifications

See Table II.

## 10. Typical Properties

### Density:

- 1.11-1.14 g/cm<sup>3</sup> at 25°C for liquid PEGs;
- 1.15-1.21 g/cm<sup>3</sup> at 25°C for solid PEGs.

### Flash point:

- 182°C for PEG 200;
- 213°C for PEG 300;
- 238°C for PEG 400;
- 250°C for PEG 600.

### Freezing point:

- < -65°C PEG 200 sets to a glass;
- 15 to -8°C for PEG 300;

- 4-8°C for PEG 400;
- 15-25°C for PEG 600.

### Melting point:

- 37-40°C for PEG 1000;
- 44-48°C for PEG 1500;
- 40-48°C for PEG 1540;
- 45-50°C for PEG 2000;
- 48-54°C for PEG 3000;
- 50-58°C for PEG 4000;
- 55-63°C for PEG 6000;
- 60-63°C for PEG 8000;
- 60-63°C for PEG 20 000.

**Moisture content:** liquid polyethylene glycols are very hygroscopic, although hygroscopicity decreases with increasing molecular weight. Solid grades, e.g., PEG 4000 and above, are not hygroscopic. See Figs. 1-3.<sup>(8)</sup>

**Particle size distribution:** see Figs. 4-7.<sup>(8)</sup>

### Refractive index:

- $n_D^{25} = 1.459$  for PEG 200;
- $n_D^{25} = 1.463$  for PEG 300;
- $n_D^{25} = 1.465$  for PEG 400;
- $n_D^{25} = 1.467$  for PEG 600.

**Solubility:** all grades of polyethylene glycol are soluble in water and miscible in all proportions with other polyethylene glycols (after melting, if necessary). Aqueous solutions of higher molecular weight grades may form gels. Liquid polyethylene glycols are soluble in acetone, alcohols, benzene, glycerin, and glycols. Solid polyethylene glycols are soluble in acetone, dichloromethane, ethanol, and methanol; they are slightly soluble in aliphatic hydrocarbons and ether, but insoluble in fats, fixed oils, and mineral oil.

**Surface tension:** approximately 44 mN/m (44 dynes/cm) for liquid polyethylene glycols; approximately 55 mN/m (55 dynes/cm) for 10% w/v aqueous solution of solid polyethylene glycol.

**Viscosity (kinematic):** see Tables III and IV.

<sup>(8)</sup> Handbook of Pharmaceutical Excipients, First Edition.

## 11. Stability and Storage Conditions

Polyethylene glycols are chemically stable in air and in solution although grades with a molecular weight less than 2000 are hygroscopic. Polyethylene glycols do not support microbial growth, nor do they become rancid.

Polyethylene glycols and aqueous polyethylene glycol solutions can be sterilized by autoclaving, filtration, or gamma irradiation.<sup>(9)</sup> Sterilization of solid grades by dry heat at 150°C for 1 hour may induce oxidation, darkening, and the formation of acidic degradation products. Ideally, sterilization should be carried out in an inert atmosphere. Oxidation of polyethylene glycols may also be inhibited by the inclusion of a suitable antioxidant.

If heated tanks are used to maintain solid polyethylene glycols in a molten state, care must be taken to avoid contamination with iron, which can lead to discoloration. The temperature must be kept to the minimum necessary to ensure fluidity; oxidation may occur if polyethylene glycols are exposed for long periods to temperatures exceeding 50°C. However, storage under nitrogen reduces the possibility of oxidation.

Polyethylene glycols should be stored in well-closed containers in a cool, dry, place. Stainless steel, aluminum, glass, or lined steel containers are preferred for the storage of liquid grades.

Table II: Pharmacopoeial specifications of polyethylene glycol.

Test	JP 400	JP 1500	JP 4000	JP 6000	JP 20 000	PhEur 300	PhEur 400	PhEur 1000	PhEur 1500	PhEur 4000	USP
Appearance of solution	—	+	+	+	+	+	+	+	+	+	+
Characteristics	—	—	—	—	—	—	—	—	—	—	—
Freezing point	—	37–41°C	53–57°C	56–61°C	56–64°C	—	—	—	—	—	—
Coagulating point	—	—	—	—	—	—	—	—	—	—	—
Viscosity	—	—	2600–3800	7300–9300	15 000–23 000	—	—	—	—	—	—
Average molecular weight	380–420	—	40–7.5	4.5–7.5	4.5–7.5	—	—	—	—	—	—
Acidifytability	+	4.0–7.0	4.0–7.0	4.5–7.5	4.5–7.5	—	—	—	—	—	—
pH (2% w/v solution)	+	4.0–7.0	4.0–7.0	4.5–7.5	4.5–7.5	—	—	—	—	—	—
Hydroxyl value	340–394	264–300	—	—	—	340–394	264–300	107–118	70–80	4.5–7.5	4.5–7.5
Reducing substances	≤ 0.1%	≤ 0.1%	≤ 0.25%	≤ 0.25%	≤ 0.25%	—	—	—	—	—	—
Residue on ignition	—	—	—	—	—	—	—	—	—	—	—
Sulfur	—	—	—	—	—	—	—	—	—	—	—
Limit of ethylene glycol and diethylene glycol	≤ 0.25%	+	—	—	—	≤ 0.4%	≤ 0.4%	≤ 0.2%	≤ 0.2%	≤ 0.2%	≤ 0.1%
Ethylene oxide	—	—	—	—	—	≤ 1 ppm	≤ 1 ppm	≤ 1 ppm	≤ 1 ppm	≤ 1 ppm	≤ 10 ppm
1,4-dioxane	—	—	—	—	—	—	—	—	—	—	≤ 10 ppm
Heavy metals	≤ 20 ppm	≤ 20 ppm	—	—	—	≤ 20 ppm	≤ 20 ppm	≤ 20 ppm	≤ 20 ppm	≤ 20 ppm	≤ 5 ppm
Organic volatile impurities	—	—	—	—	—	—	—	—	—	—	+
Water	≤ 1.0%	≤ 1.0%	≤ 1.0%	≤ 1.0%	≤ 1.0%	≤ 2.0%	≤ 2.0%	≤ 2.0%	≤ 1.0%	≤ 1.0%	—

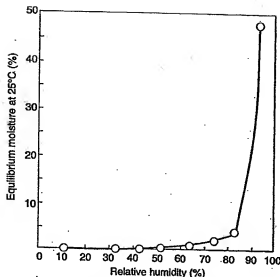


Fig. 1: Equilibrium moisture content of PEG 4000 (McKesson, Lot #B192-8209) at 25°C.

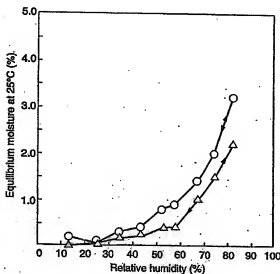


Fig. 2: Equilibrium moisture content of PEG 4000 at 25°C.  
 ○ : PEG 4000 powder (Union Carbide Corp., Lot #B-251)  
 △ : PEG E-4000 (BASF, Lot #WFPYA-573B)

## 12. Incompatibilities

The chemical reactivity of polyethylene glycols is mainly confined to the two terminal hydroxyl groups, which can be either esterified or etherified. However, all grades can exhibit some oxidizing activity due to the presence of peroxide impurities and secondary products formed by autoxidation.

Liquid and solid polyethylene glycol grades may be incompatible with some colors.

The antibacterial activity of certain antibiotics, particularly penicillin and bacitracin, is reduced in polyethylene glycol

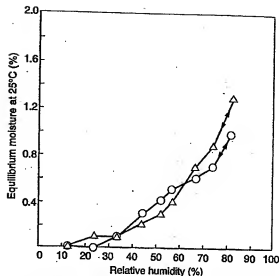


Fig. 3: Equilibrium moisture content of PEG 6000 at 25°C.  
 ○ : PEG 6000 powder (Union Carbide Corp., Lot #B-507)  
 △ : PEG E-6000 (BASF, Lot #WFPNA-124B)

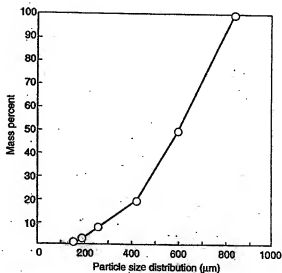


Fig. 4: Particle size distribution of PEG 4000 flakes.

bases. The preservative efficacy of the parabens may also be impaired due to binding with polyethylene glycols.

Physical effects caused by polyethylene glycol bases include softening and liquefaction in mixtures with phenol, tannic acid, and salicylic acid. Discoloration of sulfonamides and dithranol can also occur and sorbitol may be precipitated from mixtures. Plastics, such as polyethylene, phenolformaldehyde, polyvinyl chloride, and cellulose-ester membranes (in filters) may be softened or dissolved by polyethylene glycols. Migration of polyethylene glycol can occur from tablet-film coatings, leading to interaction with core components.

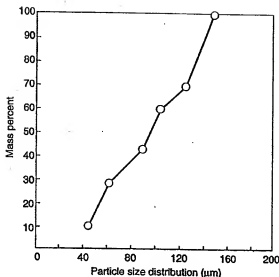


Fig. 5: Particle size distribution of PEG 4000 powder.

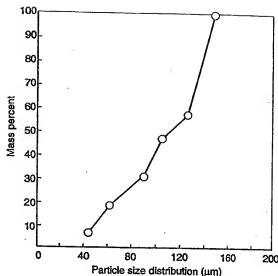


Fig. 7: Particle size distribution of PEG 6000 powder.

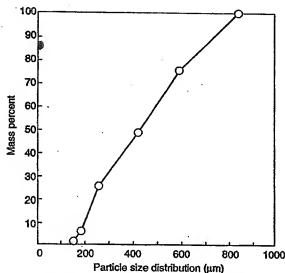


Fig. 6: Particle size distribution of PEG 6000 flakes.

### 13. Method of Manufacture

Polyethylene glycols are condensation polymers formed by the reaction of ethylene oxide and water under pressure in the presence of a catalyst.

### 14. Safety

Polyethylene glycols are widely used in a variety of pharmaceutical formulations. Generally, they are regarded as nontoxic and nonirritant materials.<sup>(10-12)</sup> However, adverse reactions to polyethylene glycols have been reported and although of relatively low toxicity, any toxicity appears to be greatest with polyethylene glycols of low molecular weight.

Polyethylene glycols administered topically may cause stinging, especially when applied to mucous membranes. Hypersensitivity reactions to polyethylene glycols applied topically, including urticaria and delayed allergic reactions, have also been reported.<sup>(13)</sup> However, the most serious adverse effects associated with polyethylene glycols are hyperosmolality, metabolic acidosis, and renal failure following the topical use of polyethylene glycols in burn patients.<sup>(14)</sup> Topical preparations containing polyethylene glycols should therefore be used cautiously in patients with renal failure, extensive burns, or open wounds.

Oral administration of large quantities of polyethylene glycols can have a laxative effect. Therapeutically, up to 4 L of an aqueous mixture of electrolytes and high molecular weight polyethylene glycol is consumed by patients undergoing bowel cleansing.<sup>(15)</sup>

Liquid polyethylene glycols may be absorbed when taken orally, but the higher molecular weight polyethylene glycols are not significantly absorbed from the gastrointestinal tract. Absorbed polyethylene glycol is excreted largely unchanged in the urine although polyethylene glycols of low molecular weight may be partially metabolized.

The WHO has set an estimated acceptable daily intake of polyethylene glycol at up to 10 mg/kg body-weight.<sup>(16)</sup>

In parenteral products, the maximum recommended concentration of PEG 300 is approximately 30% w/v since hemolytic effects have been observed at concentrations greater than about 40% v/v.

For animal toxicity data see Table V.

### 15. Handling Precautions

Observe normal precautions appropriate to the circumstances and quantity of material handled. Eye protection is recommended.

### 16. Regulatory Status

Included in the FDA Inactive Ingredients Guide (dental preparations, IM and IV injections, ophthalmic preparations, oral

Table III: Specification for viscosity of polyethylene glycol of nominal molecular weight at  $98.9^{\circ}\text{C} \pm 0.3^{\circ}\text{C}$  from the USP.

Nominal average molecular weight	Viscosity range in mm <sup>2</sup> /s (cSt)
200	3.9-4.8
300	5.4-6.4
400	6.8-8.0
500	8.3-9.6
600	9.9-11.3
700	11.5-13.0
800	12.5-14.5
900	15.0-17.0
1000	16.0-19.0
1100	18.0-22.0
1200	20.0-24.5
1300	22.0-27.5
1400	24-30
1450	25-32
1500	26-33
1600	28-36
1700	31-39
1800	33-42
1900	35-45
2000	38-49
2100	40-53
2200	43-56
2300	46-60
2400	49-65
2500	51-70
2600	54-74
2700	57-78
2800	60-83
2900	64-88
3000	67-93
3250	73-105
3350	76-110
3500	87-123
3750	99-140
4000	110-158
4250	123-177
4500	140-200
4750	155-228
5000	170-250
5500	206-315
6000	250-390
6500	295-480
7000	350-590
7500	405-735
8000	470-900

Table IV: Viscosity of selected polyethylene glycols at  $25^{\circ}\text{C}$  and  $99^{\circ}\text{C}$ .

Grade	Viscosity in mm <sup>2</sup> /s (cSt)	
	25°C	99°C
PEG 200	39.9	4.4
PEG 300	68.8	5.9
PEG 400	90.0	7.4
PEG 600	131	11.0
PEG 1000 solid	19.5	—
PEG 2000 solid	47	—
PEG 4000 solid	180	—
PEG 6000 solid	580	—
PEG 20 000 solid	6900	—

Table V: Animal toxicity data (LD<sub>50</sub>) for various grades of polyethylene glycol.<sup>(17)</sup>

PEG grade	Guinea pig (oral)	Mouse (IP)	Mouse (IV)	Mouse (oral)	LD <sub>50</sub> in g/kg Rabbit (oral)	Rabbit (SC)	Rat (IP)	Rat (IV)	Rat (oral)	Rat (SC)
PEG 200	—	7.5	—	38.3	19.9	—	—	—	28.9	—
PEG 300	19.6	—	—	—	17.3	—	17	—	27.5	—
PEG 400	15.7	10.0	8.6	28.9	26.8	—	9.7	7.3	30.2	—
PEG 810	—	—	—	—	—	—	—	13	—	16
PEG 1000	22.5	20	—	—	—	—	—	—	42	—
PEG 1540	—	—	—	—	—	—	15.4	—	51.2	—
PEG 4000	50.9	—	16	—	76	18	11.6	—	50	—
PEG 6000	50	—	—	—	—	—	6.8	—	50	—

capsules, solutions, syrups and tablets, rectal, topical, and vaginal preparations). Included in nonparenteral medicines licensed in the UK.

## 17. Pharmacopeias

Polyethylene glycols are described in many pharmacopeias.

Some pharmacopeias, such as the US, have a single monograph describing various different grades; other pharmacopeias have individual monographs. The BP for example has separate monographs for PEG 300, PEG 400, PEG 1000, PEG 1500, PEG 3000, PEG 4000, PEG 6000, PEG 20 000, and PEG 35 000.

## 18. Related Substances

Polyoxyethylene alkyl ethers; polyoxyethylene sorbitan fatty acid esters; suppository bases.

## 19. Comments

## 20. Specific References

- Hadia IA, Ugriné HE, Farouk AM, Shayonb M. Formulation of polyethylene glycol ointment bases suitable for tropical and subtropical climates I. *Acta Pharm Hung* 1989; 39: 137-142.
- Kellaway IW, Marriott C. Correlations between physical and drug release characteristics of polyethylene glycol suppositories. *J Pharm Sci* 1975; 64: 1162-1166.
- Wells JL, Bhatt DA, Khan KA. Improved wet massed tabletting using plasticized binder. *J Pharm Pharmacol* 1982; 34(Suppl): 46P.
- Chiou WL, Riegelman S. Pharmaceutical applications of solid dispersion systems. *J Pharm Sci* 1971; 60: 1281-1302.
- Ford JL, Rubinstein MH. Formulation and ageing of tablets prepared from indomethacin-polyethylene glycol 6000 solid dispersions. *Pharm Acta Helv* 1980; 55: 1-7.
- Vila-Jato JL, Blanco J, Alonso MJ. The effect of the molecular weight of polyethylene glycol on the bioavailability of paracetamol-polyethylene glycol solid dispersions. *J Pharm Pharmacol* 1986; 38: 126-128.
- Miralles MJ, McGinity JW, Martin A. Combined water-soluble carriers for coprecipitates of tolbutamide. *J Pharm Sci* 1982; 71: 302-304.

- Okhamafe AO, York P. Moisture permeation mechanism of some aqueous-based film coats. *J Pharm Pharmacol* 1982; 34(Suppl): 53P.
- Bhalla HL, Menon MR, Gopal NGS. Radiation sterilization of polyethylene glycols. *Int J Pharmaceutics* 1983; 17: 351-355.
- Smyth HF, Carpenter CP, Weil CS. The toxicology of the polyethylene glycols. *J Am Pharm Assoc (Sci)* 1950; 39: 349-354.
- Tusing TW, Elses JR, Sauveur AB. The chronic dermal toxicity of a series of polyethylene glycols. *J Am Pharm Assoc (Sci)* 1954; 43: 489-490.
- Smyth HF, Carpenter CP, Weil CS. The chronic oral toxicology of the polyethylene glycols. *J Am Pharm Assoc (Sci)* 1955; 44: 27-30.
- Fisher AA. Immediate and delayed allergic contact reactions to polyethylene glycol. *Contact Dermatitis* 1978; 4: 135-138.
- Topical PEG in burn ointments. *FDA Drug Bull* 1982; 12: 25-26.
- Parfitt K, editor. *Martindale: The Complete Drug Reference*, 32nd edition. London, Pharmaceutical Press, 1999; 1597-1598.
- FAO/WHO. Evaluation of certain food additives: twenty-third report of the joint FAO/WHO expert committee on food additives. *Tech Rep Ser Wild Hlth Org* 1980; No. 648.
- Sweet DV, editor. *Registry of Toxic Effects of Chemical Substances*. Cincinnati, US Department of Health, 1987.

## 21. General References

- Donovan MD, Flynn GL, Amidon GL. Absorption of polyethylene glycols 600 through 2000: molecular weight dependence of gastrointestinal and nasal absorption. *Pharm Res* 1990; 7: 863-867.
- Union Carbide Corporation. Technical literature: *Carbowax* polyethylene glycols, 1986.
- Van Dam J, Daenens P. Molecular weight identification of polyethylene glycols in pharmaceutical preparations by gel permeation chromatography. *J Pharm Sci* 1993; 82: 938-941.
- Yamaoka T, Tabata Y, Ikada Y. Distribution and tissue uptake of poly(ethylene glycol) with different molecular weights after intravenous administration to mice. *J Pharm Sci* 1994; 83: 601-606.

## 22. Authors

JC Price.



# Polyoxyethylene Stearates

## 1. Nonproprietary Names

The polyoxyethylene stearates are a series of polyethoxylated derivatives of stearic acid. Of the large number of different materials commercially available, two types are listed in the USP.

JP: Polyoxyyl 40 stearate

USP: Polyoxyyl 40 stearate

USP: Polyoxyyl 50 stearate

See also Sections 2, 3, 4, 5, and 17.

## 2. Synonyms

Polyoxyethylene stearates are nonionic surfactants produced by polyethoxylation of stearic acid. Two systems of nomenclature are used for these materials. The number '8' in the names 'polyoxyl 8 stearate' or 'polyoxyethylene 8 stearate' refers to the approximate polymer length in oxyethylene units. The same material may also be designated 'polyoxyethylene glycol 400 stearate' or 'macrogol stearate 400' in which case, the number '400' refers to the average molecular weight of the polymer chain.

Synonyms applicable to polyoxyethylene stearates are shown below: Ethoxylated fatty acid esters; macrogol stearates; *Marlosol*; PEG fatty acid esters; PEG stearates; polyethylene glycol stearates; poly(oxy-1,2-ethanediyl)  $\alpha$ -hydro- $\omega$ -hydroxy-octadecanoate; poly-oxyethylene glycol stearates.

Table I shows synonyms for specific materials.

## 3. Chemical Name and CAS Registry Number

Polyethylene glycol stearate [9004-99-3]

Polyethylene glycol distearate [9005-08-7]

Table I: Synonyms of selected polyoxyethylene stearates and distearates.

Name	Synonym
Polyoxyl 2 stearate	<i>Hodag DGS</i> ; PEG-2 stearate.
Polyoxyl 4 stearate	<i>Acconon 200-MS</i> ; <i>Hodag 20-S</i> ; PEG-4 stearate; polyoxyethylene (4) monostearate; polyethylene glycol 200 monostearate; <i>Protamate 200-DPS</i> .
Polyoxyl 6 stearate	<i>CeraSyn 616</i> ; <i>Kessco PEG 300 Monostearate</i> ; <i>Lipo 300S</i> ; <i>Lipo PEG 3-S</i> ; PEG-6 stearate; polyethylene glycol 300 monostearate; <i>Polystate C</i> ; polyoxyethylene (6) monostearate; <i>Protamate 300-DPS</i> .
Polyoxyl 8 stearate	<i>Acconon 400-MS</i> ; <i>CeraSyn 660</i> ; <i>Citrol 4MS</i> ; <i>Crodet 58</i> ; <i>Emerest 2640</i> ; <i>Grococ 400</i> ; <i>Hodag 40-S</i> ; <i>Kessco PEG-400 Monostearate</i> ; macrogol stearate 400; <i>Myrij 45</i> ; PEG-8 stearate; <i>Pegasperse 400 MS</i> ; polyethylene glycol 400 monostearate; polyoxyethylene (8) monostearate; <i>Protamate 400-DPS</i> ; <i>RitaSep 400 MS</i> .

(Continued)

Name	Synonym
Polyoxyl 12 stearate	<i>Hodag 60-S</i> ; <i>Kessco PEG 600 Monostearate</i> ; <i>Lipo-PEG 6-S</i> ; PEG-12 stearate; <i>Pegasperse 600 MS</i> ; polyethylene glycol 600 monostearate; polyoxyethylene (12) monostearate; <i>Protamate 600-DPS</i> .
Polyoxyl 20 stearate	<i>CeraSyn 840</i> ; <i>Hodag 100-S</i> ; <i>Kessco PEG 1000 Monostearate</i> ; <i>Lipo-PEG 10-S</i> ; <i>Myrij 49</i> ; <i>Pegasperse 1000 MS</i> ; PEG-20 stearate; polyethylene glycol 1000 monostearate; polyoxyethylene (20) monostearate; <i>Protamate 1000-DPS</i> .
Polyoxyl 30 stearate	<i>Myrij 51</i> ; PEG-30 stearate; polyoxyethylene (30) stearate.
Polyoxyl 40 stearate	<i>Crodet 840</i> ; <i>E431</i> ; <i>Emerest 2672</i> ; <i>Hodag POE (40) MS</i> ; <i>Lipal 395</i> ; macrogol stearate 2000; <i>Myrij 52</i> ; PEG-40 stearate; polyoxyethylene glycol 2000 monostearate; polyoxyethylene (40) monostearate; <i>Protamate 2000-DPS</i> .
Polyoxyl 50 stearate	<i>Atlas G-2153</i> ; <i>Crodet 530</i> ; <i>Lipal 505</i> ; <i>Myrij 53</i> ; PEG-50 stearate; polyoxyethylene (50) monostearate.
Polyoxyl 100 stearate	<i>Myrij 59</i> ; PEG-100 stearate; polyethylene glycol 4400 monostearate; polyoxyethylene (100) monostearate; <i>Protamate 4400-DPS</i> .
Polyoxyl 150 stearate	<i>Hodag 600-S</i> ; PEG-150 stearate.
Polyoxyl 4 distearate	<i>Hodag 22-S</i> ; PEG-4 distearate.
Polyoxyl 8 distearate	<i>Hodag 42-S</i> ; <i>Kessco PEG 400 DS</i> ; PEG-8 distearate; polyethylene glycol 400 distearate; <i>Protamate 400-DS</i> .
Polyoxyl 12 distearate	<i>Hodag 62-S</i> ; <i>Kessco PEG 600 Distearate</i> ; PEG-12 distearate; polyethylene (12) distearate; polyethylene glycol 600 distearate; <i>Protamate 600-DS</i> .
Polyoxyl 32 distearate	<i>Hodag 154-S</i> ; <i>Kessco PEG 1540 Distearate</i> ; PEG-32 distearate; polyethylene glycol 1540 distearate; polyoxyethylene (32) distearate.
Polyoxyl 150 distearate	<i>Hodag 602-S</i> ; <i>Kessco PEG 6000 DS</i> ; PEG-150 distearate; polyethylene glycol 6000 distearate; polyoxyethylene (150) distearate; <i>Protamate 6000-DS</i> .

## 4. Empirical Formula Molecular Weight

See Table II.


Table II: Empirical formula and molecular weight of selected polyoxyethylene stearates.

Name	Empirical Formula	Molecular Weight
Polyoxyl 6 stearate	$C_{30}H_{60}O_8$	548.80
Polyoxyl 8 stearate	$C_{38}H_{76}O_{10}$	636.91
Polyoxyl 12 stearate	$C_{50}H_{100}O_{14}$	813.12
Polyoxyl 20 stearate	$C_{70}H_{140}O_{22}$	1165.55
Polyoxyl 40 stearate	$C_{130}H_{260}O_{42}$	2046.61
Polyoxyl 50 stearate	$C_{165}H_{330}O_{52}$	2487.15
Polyoxyl 100 stearate	$C_{330}H_{660}O_{102}$	4689.80

## 5. Structural Formula



For the monostearate; where the average value of  $n$  is 6 for polyoxyl 6 stearate, 8 for polyoxyl 8 stearate, etc.



For the distearate; where the average value of  $n$  is 12 for polyoxyl 12 distearate, 32 for polyoxyl 32 distearate, etc.

In both structures, R represents the alkyl group of the parent fatty acid. With stearic acid, R is  $\text{CH}_3(\text{CH}_2)_{16}$ . However, it should be noted that stearic acid usually contains other fatty acids, primarily palmitic acid, and consequently a polyoxyethylene stearate may also contain varying amounts of other fatty acid derivatives such as palmitates.

## 6. Functional Category

Emulsifying agent; solubilizing agent; wetting agent.

## 7. Applications in Pharmaceutical Formulation or Technology

Polyoxyethylene stearates are generally used as emulsifiers in oil-in-water-type creams and lotions. Their hydrophilicity or lipophilicity depends on the number of ethylene oxide units present: the larger the number, the greater the hydrophilic properties. Polyoxyl 40 stearate has also been used as an emulsifying agent in intravenous infusions.<sup>(1)</sup>

Polyoxyethylene stearates are particularly useful as emulsifying agents when astringent salts or other strong electrolytes are present. They can also be blended with other surfactants to obtain any hydrophilic-lipophilic balance for lotions or ointment formulations.

Use	Concentration (%)
Auxiliary emulsifier for o/w intravenous fat emulsion	0.5-5
Emulsifier for o/w creams or lotions	0.5-10
Ophthalmic ointment	7
Suppository component	1-10
Tablet lubricant	1-2

## 8. Description

Name	Description
Polyoxyl 6 stearate	Soft solid
Polyoxyl 8 stearate	Waxy cream
Polyoxyl 12 stearate	Pasty solid
Polyoxyl 20 stearate	Waxy solid
Polyoxyl 40 stearate	Waxy solid, with a faint, bland, fat-like odor, off-white to light tan in color.
Polyoxyl 50 stearate	Solid, with a bland, fat-like odor or odorless.
Polyoxyl 100 stearate	Solid
Polyoxyl 12 distearate	Paste
Polyoxyl 32 distearate	Solid
Polyoxyl 150 distearate	Solid

## 9. Pharmacopeial Specifications

Test	JP Polyoxyl 40 stearate	USP Polyoxyl 40 stearate	USP Polyoxyl 50 stearate
Identification	—	+	+
Characters	+	—	—
Clarity and color of solution	+	—	—
Coagulating range	39.0-44.0°C	37-47°C	—
Coagulating point of the fatty acid	≥ 53 °C	—	—
Residue on ignition	≤ 0.10%	—	—
Water	—	≤ 3.0%	≤ 3.0%
Arsenic	≤ 3 ppm	—	≤ 3 ppm
Heavy metals	≤ 10 ppm	≤ 0.001%	≤ 0.001%
Acid value	≤ 1	≤ 2	≤ 2
Hydroxyl value	—	25-40	23-35
Saponification value	25-35	25-35	20-28
Free polyoxyethylene glycols	—	17-27%	17-27%
Organic volatile impurities	—	+	+

## 10. Typical Properties

Flash point:

> 149°C for polyoxyl 8 stearate (Myrj 45).

Solubility:

Name	Solvent		
	Ethanol (95%)	Mineral oil	Water
Polyoxyl 6 stearate	S	S	DH
Polyoxyl 8 stearate	S	I	D
Polyoxyl 12 stearate	S	I	S
Polyoxyl 20 Stearate	S	I	S
Polyoxyl 40 stearate	S	I	S
Polyoxyl 50 stearate	S	I	S
Polyoxyl 100 stearate	S	I	S
Polyoxyl 12 distearate	S	—	DH
Polyoxyl 32 distearate	S	—	S
Polyoxyl 150 distearate	I	—	S

Where,

D = dispersible

S = soluble

I = insoluble

DH = dispersible (with heat)

See also Table III.

## 11. Stability and Storage Conditions

Polyoxyethylene stearates are generally stable in the presence of electrolytes and weak acids or bases. Strong acids and bases can cause gradual hydrolysis and saponification.

The bulk material should be stored in a well-closed container, in a dry place, at room temperature.

## 12. Incompatibilities

Polyoxyethylene stearates are unstable in hot alkaline solutions due to hydrolysis, and will also saponify with strong acids or bases. Discoloration or precipitation can occur with salicylates, phenolic substances, iodine salts, and salts of bismuth, silver, and tannins.<sup>(2-4)</sup> Complex formation with preservatives may also occur.<sup>(5)</sup>

Table III: Typical properties of polyoxyethylene stearates.

Name	Acid value	Free ethylene oxide	HLB value	Hydroxyl value	Iodine number	Melting point (°C)	Saponification value	Water content (%)
Polyoxyl 6 stearate	≤ 5.0	≤ 100 ppm	9.7	—	≤ 0.5	28-32	95-110	—
Polyoxyl 8 stearate	≤ 2.0	≤ 100 ppm	11.1	87-105	≤ 1.0	28-33	82-95	≤ 3.0
Polyoxyl 12 stearate	≤ 8.5	≤ 100 ppm	13.6	55-75	≤ 1.0	≈ 37	62-78	≤ 1.0
Polyoxyl 20 stearate	≤ 1.0	≤ 100 ppm	14	50-62	≤ 1.0	≈ 28	46-56	≤ 1.0
Polyoxyl 30 stearate	≤ 2.0	—	16	35-50	—	—	30-45	≤ 3.0
Polyoxyl 40 stearate	≤ 1.0	—	16.9	27-40	—	≈ 38	25-35	≤ 3.0
Polyoxyl 50 stearate	≤ 2.0	—	17.9	23-35	—	≈ 42	20-28	≤ 3.0
Polyoxyl 100 stearate	≤ 1.0	≤ 100 ppm	18.8	15-30	—	≈ 46	9-20	≤ 3.0
Polyoxyl 8 distearate	≤ 10.0	—	—	≤ 15	≤ 0.5	≈ 36	115-124	—
Polyoxyl 12 distearate	≤ 10.0	≤ 100 ppm	10.6	≤ 20	≤ 1.0	≈ 39	93-102	≤ 1.0
Polyoxyl 32 distearate	≤ 10.0	≤ 100 ppm	14.8	≤ 20	≤ 0.25	≈ 45	50-62	≤ 1.0
Polyoxyl 150 distearate	7-9	≤ 100 ppm	18.4	≤ 15	≤ 0.1	53-57	14-20	≤ 1.0

The antimicrobial activity of some materials such as bacitracin, chloramphenicol, phenoxymethylpenicillin, sodium penicillin, and tetracycline may be reduced in the presence of polyoxyethylene stearate concentrations greater than 5% w/w.<sup>(6,7)</sup>

### 13. Method of Manufacture

Polyoxyethylene stearates are prepared by the direct reaction of fatty acids, particularly stearic acid, with ethylene oxide.

### 14. Safety

Although polyoxyethylene stearates are primarily used as emulsifying agents in topical pharmaceutical formulations certain materials, particularly polyoxyl 40 stearate, have also been used in intravenous injections and oral preparations.<sup>(1,4)</sup>

Polyoxyethylene stearates have been extensively tested for toxicity in animals<sup>(8-12)</sup> and are widely used in pharmaceutical formulations and cosmetics. They are generally regarded as essentially nontoxic and nonirritant materials.

#### Polyoxyl 8 stearate:

LD<sub>50</sub> (hamster, oral): 27 g/kg<sup>(14)</sup>

LD<sub>50</sub> (rat, oral): 64 g/kg

#### Polyoxyl 20 stearate:

LD<sub>50</sub> (mouse, IP): 0.2 g/kg<sup>(14)</sup>

LD<sub>50</sub> (mouse, IV): 0.87 g/kg

### 15. Handling Precautions

Observe normal precautions appropriate to the circumstances and quantity of material handled.

Polyoxyethylene stearates that contain greater than 100 ppm of free ethylene oxide may present an explosion hazard when stored in a closed container. This is due to the release of ethylene oxide into the container headspace where it can accumulate, and so exceed the explosion limit.

### 16. Regulatory Status

Included in the FDA Inactive Ingredients Guide (dental solutions, IV injections, ophthalmic preparations, oral capsules and tablets, otc suspensions, topical creams, emulsions, lotions, ointments and solutions, and vaginal preparations). Included in nonparenteral medicines licensed in the UK.

### 17. Pharmacopelias

Name	Pharmacopelias
Polyoxyl 40 stearate	Jpn. US.
Polyoxyl 50 stearate	US.

### 18. Related Substances

Polyethylene glycol; stearic acid.

### 19. Comments

### 20. Specific References

- Cohn I, Singleton S, Hartwig QL, Atik M. New intravenous fat emulsion. *JAMA* 1963; 183: 755-757.
- Thoma K, Ullmann E, Fickel O. The antibacterial activity of phenols in the presence of polyoxyethylene stearates and polyethylene glycols [in German]. *Arch Pharm* 1970; 303: 289-296.
- Thoma K, Ullmann E, Fickel O. Dimensions and cause of the reaction between phenols and polyoxyethylene stearates [in German]. *Arch Pharm* 1970; 303: 297-304.
- Duchêne D, Djiane A, Puisieux F. Tablet study III: influence of nonionic surfactants with ester linkage on the quality of sulfanilamide grains and tablets [in French]. *Ann Pharm Fr* 1970; 28: 289-298.
- Chakravarty D, Lach JL, Blaug SM. Study of complex formation between polyoxyl 40 stearate and some pharmaceuticals. *Drug Standards* 1957; 25: 137-140.
- Ullmann E, Moser B. Effect of polyoxyethylene stearates on the antibacterial activity of antibiotics [in German]. *Arch Pharm* 1962; 295: 136-143.
- Thoma K, Ullmann E, Zeifert G. Investigation of the stability of penicillin G sodium in the presence of nonionic surface active agents (polyethylene glycol derivatives) [in German]. *Arch Pharm* 1962; 295: 670-678.
- Culver PJ, Wilcox CS, Jones CM, Rose RS. Intermediary metabolism of certain polyoxyethylene derivatives in man I: recovery of the polyoxyethylene moiety from urine and feces following ingestion of polyoxyethylene (20) sorbitan monooleate and of polyoxyethylene (40) mono-stearate. *J Pharmacol Exp Ther* 1951; 103: 377-381.